

Local Quasiparticle States around an Anderson Impurity in a d -Wave Superconductor: Kondo Effects

Jian-Xin Zhu and C. S. Ting

Texas Center for Superconductivity and Department of Physics, University of Houston, Houston, Texas 77204

The mutual influence between a Kondo impurity and a d -wave superconductor is numerically studied within the slave-boson mean-field approach. The Bogoliubov-de Gennes type equations are derived and solved using exact diagonalization. We show that a critical coupling strength, above which the Kondo effect takes place, exists regardless of whether the band particle-hole symmetry is present or not. In the Kondo regime the double resonant quasiparticle peaks are found in the local density of states (LDOS) both directly at the impurity and around its neighbors, which is in sharp contrast to the case of nonmagnetic unitary impurities, where the LDOS vanishes at the impurity site.

PACS numbers: 74.25.Jb, 72.15.Qm, 74.50.+r, 73.20.Hb

The identification of d -wave pairing state in high- T_c superconductors [1] has renewed much interest in low-energy quasiparticle states in unconventional superconductors. Different from conventional s -wave superconductors having a constant energy gap, the d -wave superconductors have an anisotropic energy gap which changes sign along the nodal directions on the essentially cylindrical Fermi surface. The anisotropy of the energy gap makes the d -wave superconductors very sensitive to impurity or other potential scattering, in contrast to the s -wave superconductors which, as dictated by the Anderson theorem [2], are almost unaffected by the presence of nonmagnetic impurities. As an important signature of the sign change of d -wave order parameter (OP), Balatsky, Salkola and co-workers [3,4], based on the T-matrix approximation, theoretically predicted that a strong atomic-like nonmagnetic impurity can induce a virtual bound state. Later studies [5,6] showed that the resonant state would show up in the local density of states (LDOS), which could be measured by the local differential tunneling conductance. Recent scanning tunneling spectroscopy measured on high- T_c superconductor $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ (BSCCO) with individual atomic-scale defects [7] or strong impurities [8,9], has provided strong evidence for the existence of low-energy quasi-bound states. Especially, the experiment by Pan *et al.* [9] on the observation of quasiparticle resonant states has a high spatial and energy resolution and the identity of impurity atoms is known in a controlled way. Very interestingly, the imaging of the effect of a single zinc (Zn) impurity atom showed the strongest intensity of the LDOS at resonance directly on the Zn atom, which is opposite to the earlier theories [3–6]. In our previous work [10], we explained the novel pattern of the tunneling conductance in terms of the blocking effect of the BiO and SrO layers which exist between the tunneling tip and the CuO_2 layer being probed. This explanation may not exclude other possibilities and needs further experimental justification [11]. Although almost all existing theories are treating the Zn atom as a static potential scatterer, there exists a few experiments [12] indicating that Zn impurity

may possess a magnetic moment. It is now an appropriate time to consider the effects of dynamic impurities on the quasiparticle properties of d -wave superconductors. The study of a dynamic impurity in a superconductor began with the works of Yu [13] and Shiba [14] on magnetic impurities in s -wave systems. The solving of this problem is quite challenging mainly due to the difficulty in treating the dynamical correlations of the coupled impurity-conduction electron system with pair correlation. The problem of Kondo impurities in a d -wave system has been studied by focusing on either the moment formation [15,16] or the suppression of superconducting transition temperature by them [17]. Quite recently, within a Kondo spin model, Tsuchiura *et al.* [18] have studied the LDOS around a magnetic impurity by treating the impurity spin as an effective local magnetic field and the screening of the impurity spin by the quasiparticles was not considered there. However, other new theories [19,20] argued that the moment may be screened deep in a d -wave superconducting state. Experimentally, the specific heat measurement of Zn-doped $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ [21] provided a possible evidence of Kondo screening in the superconducting state.

In this paper we study the Kondo effects of an Anderson impurity coupled with the conduction electrons of a d -wave superconductor. Within a slave-boson mean-field approach, we are able to exactly solve the composite system with the self-consistency for the d -wave OP included. It is shown that a critical coupling strength, above which the Kondo effect emerges, exists regardless of the band particle-hole (PH) symmetry being present or not. We also show in the Kondo regime that a double resonant-peak structure shows up in the LDOS both at the impurity and at its nearest neighboring sites. This result is different from those for the static impurities that the LDOS at the impurity site exhibits only a single peak below (or above) the Fermi energy for a weak repulsive (or attractive) scattering center while vanishes in the unitary scattering limit.

To describe the impurity and its interaction with the band electrons of the d -wave superconductor defined on

a two-dimensional lattice, we start with an Anderson-like Hamiltonian, which consists of three parts: $H = H_S + H_{imp} + H_{S-imp}$. Here $H_S = -\sum_{\mathbf{i},\sigma} (t_{\mathbf{i}\mathbf{j}} + \mu\delta_{\mathbf{i}\mathbf{j}}) c_{\mathbf{i}\sigma}^\dagger c_{\mathbf{j}\sigma} + \sum_{\mathbf{i}\mathbf{j}} (\Delta_{\mathbf{i}\mathbf{j}} c_{\mathbf{i}\uparrow}^\dagger c_{\mathbf{j}\downarrow}^\dagger + \Delta_{\mathbf{i}\mathbf{j}}^* c_{\mathbf{j}\downarrow} c_{\mathbf{i}\uparrow}) + \sum_{\mathbf{i} \neq \mathbf{j}} \frac{|\Delta_{\mathbf{i}\mathbf{j}}|^2}{g_{\mathbf{i}\mathbf{j}}}$, is the Hamiltonian for the host d -wave superconductor, where $c_{\mathbf{i}\sigma}^\dagger$ ($c_{\mathbf{i}\sigma}$) are the creation (annihilation) operators of a conduction electron with spin σ at the $\mathbf{i}$ th site, $t_{\mathbf{i}\mathbf{j}}$ is the hopping integral between two nearest neighbor sites, μ is the chemical potential, $g_{\mathbf{i}\mathbf{j}}$ represents the strength of d -wave pairing interaction, and $\Delta_{\mathbf{i}\mathbf{j}}$ is the bond pairing amplitude which is in turn determined self-consistently as $\Delta_{\mathbf{i}\mathbf{j}} = g_{\mathbf{i}\mathbf{j}} \langle c_{\mathbf{i}\uparrow}^\dagger c_{\mathbf{j}\downarrow}^\dagger \rangle$; $H_{imp} = \sum_{\sigma} \epsilon_d d_{\sigma}^\dagger d_{\sigma} + U n_{d\uparrow} n_{d\downarrow}$ is the Hamiltonian for the Anderson impurity, where $d_{\sigma}^\dagger$ (d_{σ}) is the creation (annihilation) operator of the impurity electron with spin σ , $n_{d\sigma} = d_{\sigma}^\dagger d_{\sigma}$, ϵ_d is the bare impurity energy level with respect to the chemical potential of band electrons, and U is the on-site repulsive interaction of the impurity electrons; and $H_{S-imp} = \mathcal{V} \sum_{\sigma} (c_{\mathbf{i}=\mathbf{0}+\boldsymbol{\delta},\sigma}^\dagger d_{\sigma} + d_{\sigma}^\dagger c_{\mathbf{i}=\mathbf{0}+\boldsymbol{\delta},\sigma})$ represents the hybridization of the impurity with the conduction electrons, where without loss of generality, we have chosen the impurity to be located at the origin $\mathbf{i} = \mathbf{0}$, $\boldsymbol{\delta}$ are the unit vectors of the square lattice, and $\mathcal{V}$ is the coupling strength. For our purpose of studying the low temperature physics, we assume that the on-site interaction U is infinite so that the double occupancy on the impurity is forbidden, which allows us to apply the slave-boson mean-field theory [22]. This approach has been applied successfully to the low-temperature properties of a Kondo impurity in the presence of normal state conduction electrons [23], and to transport properties of a quantum dot connected to a normal and to a (conventional) superconducting lead [24,25], or embedded into a (conventional) Josephson junction [26]. By writing the impurity electron operator as $d_{\sigma} = b^\dagger f_{\sigma}$, where f_{σ} and b are the spinon and holon operators and subject to the single occupancy constraint $\sum_{\sigma} f_{\sigma}^\dagger f_{\sigma} + b^\dagger b = 1$, in the mean-field approximation, we are able to obtain $H_{imp} = \sum_{\sigma} (\epsilon_d + \lambda_0) f_{\sigma}^\dagger f_{\sigma} + \lambda_0 (b_0^2 - 1)$, and $H_{S-imp} = \mathcal{V} b_0 \sum_{\sigma} (c_{\mathbf{i}=\mathbf{0}+\boldsymbol{\delta},\sigma}^\dagger f_{\sigma} + f_{\sigma}^\dagger c_{\mathbf{i}=\mathbf{0}+\boldsymbol{\delta},\sigma})$. Here the holon operator b has been replaced by a c -number b_0 , λ_0 is the Lagrange multiplier introduced to enforce the single occupancy constraint. Then the composite Hamiltonian can be diagonalized by performing the canonical transformation for both the conduction and the impurity electrons, which leads to the Bogoliubov-de Gennes equations:

$$\sum_{\mathbf{j}} \begin{pmatrix} H_{\mathbf{i}\mathbf{j}} & \Delta_{\mathbf{i}\mathbf{j}} \\ \Delta_{\mathbf{i}\mathbf{j}}^* & -H_{\mathbf{i}\mathbf{j}} \end{pmatrix} \begin{pmatrix} u_{\mathbf{j}}^n \\ v_{\mathbf{j}}^n \end{pmatrix} = E_n \begin{pmatrix} u_{\mathbf{i}}^n \\ v_{\mathbf{i}}^n \end{pmatrix}, \quad (1)$$

where $(u_{\mathbf{i}}^n, v_{\mathbf{i}}^n)^{\text{Transpose}}$ is the quasiparticle wavefunction with eigenvalue E_n ,

$$H_{\mathbf{i}\mathbf{j}} = -\tilde{t}_{\mathbf{i}\mathbf{j}} - \mu\delta_{\mathbf{i}\neq\mathbf{0},\mathbf{j}} + (\epsilon_d + \lambda_0)\delta_{\mathbf{i}\mathbf{0}}\delta_{\mathbf{i}\mathbf{j}}, \quad (2)$$

with $\tilde{t}_{\mathbf{i}\mathbf{j}} = \mathcal{V}b_0$ for $(\mathbf{i}\mathbf{j}) = (\boldsymbol{\delta}\mathbf{0})$ or $(\mathbf{0}\boldsymbol{\delta})$ and t otherwise, $\Delta_{\mathbf{i}\mathbf{j}}$ and b_0 are subject to the self-consistent condition,

$$\Delta_{\mathbf{i}\mathbf{j}} = \frac{g_{\mathbf{i}\mathbf{j}}}{2} \sum_n (u_{\mathbf{i}}^n v_{\mathbf{j}}^{n*} + u_{\mathbf{j}}^n v_{\mathbf{i}}^{n*}) \tanh(E_n/2k_B T), \quad (3)$$

and

$$b_0^2 = 1 - 2 \sum_n \{ |u_{\mathbf{0}}^n|^2 f(E_n) + |v_{\mathbf{0}}^n|^2 [1 - f(E_n)] \}, \quad (4)$$

with $f(E) = [1 + \exp(E/k_B T)]^{-1}$ the Fermi distribution function. Here we have assumed the conduction and the impurity electrons are of different nature and take the pairing interaction $g_{\mathbf{i}\mathbf{j}} = 0$ between them, and otherwise $g_{\mathbf{i}\mathbf{j}} = g$ to be a constant. Notice that the eigenvalues and the corresponding eigenfunction amplitudes in Eq. (4) is implicitly λ_0 -dependent. The single occupancy constraint, as given by Eq. (4), is not sufficient to determine the values of b_0 and λ_0 . For this purpose, we need to minimize the free energy, which is derived for the first time in terms of the quasiparticle wavefunction as:

$$\begin{aligned} F = 2k_B T \sum_n \ln[1 - f(E_n)] - \sum_n \sum_{\mathbf{i},\mathbf{j}} [\Delta_{\mathbf{i}\mathbf{j}} u_{\mathbf{j}}^{n*} v_{\mathbf{i}}^n + \text{c.c.}] \\ + \sum_n \sum_{\mathbf{i},\mathbf{j}} \{ [-\tilde{t}_{\mathbf{i}\mathbf{j}} + (\epsilon_d + \lambda_0)\delta_{\mathbf{i}\mathbf{0}}\delta_{\mathbf{i}\mathbf{j}} - \mu\delta_{\mathbf{i}\neq\mathbf{0},\mathbf{j}}] v_{\mathbf{j}}^n v_{\mathbf{i}}^{n*} + \text{c.c.} \} \\ + \sum_{\mathbf{i}\mathbf{j}} \frac{|\Delta_{\mathbf{i}\mathbf{j}}|^2}{g_{\mathbf{i}\mathbf{j}}} + \lambda_0 (b_0^2 - 1). \end{aligned} \quad (5)$$

This minimization will give two equations for λ_0 and b_0 , one of which is just the single occupancy constraint Eq. (4). When applied to other physical problems, this expression for the free energy is very useful in determining the stability of competing pairing states.

Equation (1) always has a trivial solution with $\lambda_0 = -\epsilon_d$ and $b_0 = 0$, which describes the impurity decoupled with the conduction electrons. This trivial critical point can be shown not necessarily to have the lowest free energy. We solve Eq. (1) by taking λ_0 as a fixed parameter, and calculate the free energy with the obtained value of b_0 and $\Delta_{\mathbf{i}\mathbf{j}}$. By varying the value of λ_0 and repeating the same procedure, we obtain the free energy as a function of λ_0 . Comparing the minimum free energy with that of $\lambda_0 = -\epsilon_d$ and $b_0 = 0$, the true solution for λ_0 and b_0 is then determined. The numerical calculation is performed on a square lattice with size $N_L = N_x \times N_y = 35 \times 35$ and averaged over 36 wavevectors in the supercell Brillouin zone. Throughout the work, we are interested in the zero temperature limit, and take the pairing interaction $g = 2t$, the bare impurity level $\epsilon_d = -2t$. With respect to the real materials, this value of g leads to an exaggerated amplitude of the energy gap. Our choice of the parameters is motivated by the desire to have a short coherence length. The calculations with smaller values of energy gap have shown similar results and no qualitative changes appear. In Fig. 1, we plot b_0 and the free energy per site as a function of λ_0 for various values of the coupling strength $\mathcal{V}$. Also shown is the value of the

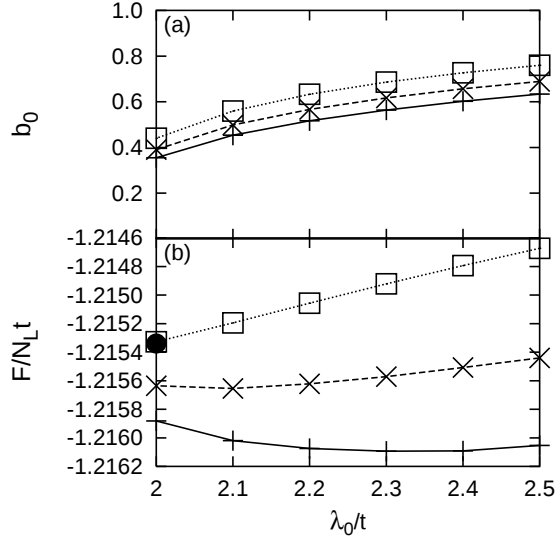


FIG. 1. The parameter b_0 (a) and the free energy per site as a function of the Lagrange multiplier λ_0 for the coupling strength $\mathcal{V} = 1.0t$ (solid line), $0.8t$ (dashed line), and $0.6t$ (dotted line). Also shown in (b) the value of $F/N_L t$ with $\lambda_0 = 2t$ and $b_0 = 0$ (filled circle). The chemical potential $\mu = -0.5t$, the bare impurity level $\epsilon_d = -2t$, the d -wave pairing interaction $g = 2t$.

free energy F_0 obtained with $\lambda_0 = -\epsilon_d$ and $b_0 = 0$, which is independent of $\mathcal{V}$. We find a critical value $V_c \approx 0.6t$ for both $\mu = -0.5$ and 0 , below which the minimum free energy is larger than F_0 . In this regime, the impurity is decoupled with conduction band, and the electron on the impurity site is described by the spinon only. When $\mathcal{V} > V_c$, this free local spin state is unstable against the coupling to the conduction electrons. We find: For the coupling strength $\mathcal{V} = 1.0t$, $0.8t$, and $0.6t$, respectively, $(\lambda_0, b_0) = (2.3t, 0.56)$, $(2.1t, 0.50)$, and $(2t, 0)$ for $\mu = -0.5t$, which breaks the band PH symmetry; while $(\lambda_0, b_0) = (2.4t, 0.59)$, $(2.1t, 0.42)$, and $(2.0t, 0)$ for $\mu = 0$, which conserves the band PH symmetry. Our numerical result is consistent with the conclusion by Withoff and Fradkin [27] based on the Kondo exchange model that if the DOS of the conduction band vanishes linearly at the Fermi energy, the Kondo effect is suppressed for small values of the coupling constant. However, for the special case where the band PH symmetry is present, the critical coupling strength is still found to be finite. At a first glance, our result seems to differ from the earlier prediction based on the Kondo spin model by Ingersent [28] that for the PH symmetry case the Kondo effect is absent for all values of coupling. The discrepancy with Ref. [28] may come from the facts that: (i) in the present model, the local PH symmetry is still broken due to the asymmetric Anderson impurity and/or the single-occupancy constraint; (ii) the existence of the Kondo effect is sensitive to the local character of conduction electrons near the impurity; and the magnetic property of the impurity and the quasiparticle properties of superconductors

interplay with each other, that is, the presence of the impurity enhances the LDOS of the d -wave superconductor (as shown below), which in turn screens the impurity spin.

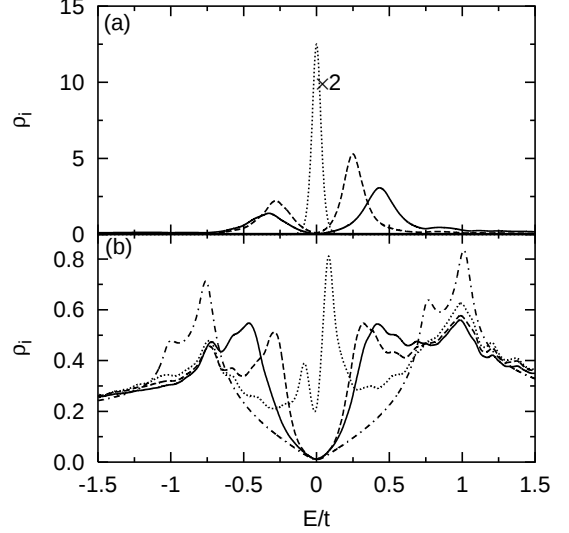


FIG. 2. The local density of states directly at the impurity site (a) and its nearest neighbor (b) for the coupling strength $\mathcal{V} = 1t$ (solid line), $0.8t$ (dashed line), and $0.6t$ (dotted line). Also shown in (b) the bulk density of states (dash-dotted line). The chemical potential $\mu = -0.5t$.

Once the parameter values of λ_0 and b_0 , and the OP are obtained, the local density of states is then calculated according to

$$\rho_i = 2 \sum_n [|u_i^n|^2 \delta(E_n - E) + |v_i^n|^2 \delta(E_n + E)], \quad (6)$$

which is proportional to the local differential tunneling conductance as measured by the STM. Figure 2 shows the LDOS as a function of energy at the impurity site and its nearest neighbor with $\mu = -0.5t$. Also shown in Fig. 2(b) is the bulk density of states in the absence of the impurity. In the bulk DOS, the superconducting coherent peaks are exhibited at the gap edge $\pm\Delta_g (= 0.75t)$. The peaks outside the gap comes from the Van Hove singularity. Due to the finite magnitude of the PH symmetry breaking by $\mu \neq 0$, the spectrum both inside and outside the gap is asymmetric with respect to $E = 0$. More interestingly, within the energy gap, the resonant peaks show up in the LDOS both at the impurity site and its nearest neighbors, in sharp contrast to the unitary nonmagnetic impurity case where the LDOS vanishes at the impurity site [4,10]. The appearance of the double-peak structure in the LDOS directly at the impurity site also makes the result different from the weak nonmagnetic impurity case where only one peak appears below or above the Fermi energy ($E = 0$) when the scattering is repulsive or attractive [4,10]. The difference is mainly due to the fact that, in addition to a weak nonmagnetic-like impurity

scattering in the Kondo resonance phase regime, there is also a disruption of the effective hopping as given by $\mathcal{V}b_0$ (from the point of view of the conduction electrons), immediately connecting the impurity site. The decrease of $\mathcal{V}$ enhances the quasiparticle scattering near the impurity by the suppression of $\mathcal{V}b_0$ on one hand and shifts the impurity level to $\tilde{\epsilon}_d = \epsilon_d + \lambda_0$ to the Fermi surface on

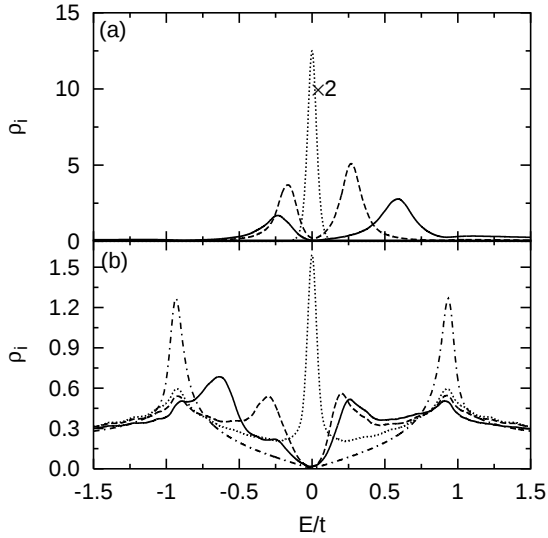


FIG. 3. Same as Fig. 2 but with $\mu = 0$.

the other hand. As a consequence of this decrease: (i) At the impurity site, the Kondo resonance peaks are sharpened with their separation decreased, and finally the double peaks merge into a single peak as $\mathcal{V}$ approaches $\mathcal{V}_c$ at which the decoupling of the impurity from the conduction band takes place; (ii) At the nearest neighbor to the impurity site, the separation between double peaks is also decreased but the double-peak structure still survives when $\mathcal{V} = \mathcal{V}_c$, which is intrinsic to a d -wave superconductor with a short coherence when the PH symmetry is broken to some extent [29]. When the band PH symmetry is conserved ($\mu = 0$), as shown in Fig. 3, we see that most features of the local electronic structure are similar to the case with $\mu \neq 0$ except that the spectrum is now symmetric outside the gap (but still asymmetric inside the gap due to the breaking of the local PH symmetry) and that at the nearest neighbor to the impurity only exhibits a single zero-energy peak when $\mathcal{V} = \mathcal{V}_c$. We have also studied the case with different values of impurity level ϵ_d and found similar results.

Two remarks are in order: (1) Although the slave-boson mean field theory captures the essential physics in the Kondo resonance regime, where a spin-singlet state is formed, unfortunately, it is unable to identify the quantum transition from the spin-singlet state (screened impurity spin) to the spin-doublet state (unscreened impurity spin). The slave-boson mean field solution always leads to a lower energy in the spin-singlet state

than in the spin-doublet state [26]. One must go beyond the static mean-field level and employ alternatively the non-crossing approximation to describe this transition [25]. (2) Very recently, Polkovnikov *et al.* [30] have studied a similar problem. The difference and similarity between two works are as follows. The difference: (i) In their work, the Kondo exchange model where the impurity spin is coupled to the spin of conduction electrons. These two models should be equivalent, but the methods to solve them are different; (ii) In addition to the first nearest-neighbor hopping (t), second (t') and the third (t'') nearest-neighbor hopping were also introduced in their model. Instead only the first nearest-neighbor hopping is used in the present work; (iii) In their work, the modification of the superconductivity by the Kondo impurity was neglected, while in the present work, this effect has been taken into account by our self-consistent calculation; (iv) A vanishing density of states near zero bias at the sites nearest neighboring to the impurity was obtained in their work, while in the present work, the intensity of density of states on these sites was found to be significant. The similarity: (i) Both works have shown the split peaks for the local density of states directly on the impurity site; (ii) The models in both papers are placing the magnetic moment at the impurity site. This is different from the experimental situation for high- T_c superconductors with Zn impurities where the magnetic spin would most likely be induced at sites nearest-neighboring to the Zn impurity. Therefore, these two models might be more suitable to describe the effects of Kondo impurities such as Mn, Fe, Co substituted for Cu in high- T_c cuprates.

In summary, we have considered the problem of an Anderson impurity coupled to the conduction electrons of a d -wave superconductor. Within a slave-boson mean-field approach, we have been able to exactly diagonalize the composite Hamiltonian with the pair breaking effect taken into account. A critical coupling strength, above which the Kondo phase occurs, is found regardless of whether the PH symmetry is present. In the Kondo effect regime, the double-peak structure appears at both the impurity site and its nearest neighboring sites. Our analysis seems to indicate that the spatial pattern of the differential tunneling conductance around a Zn impurity in BSCCO [9] cannot be fully explained with the Kondo impurity model.

Acknowledgments: We thank G. Kotliar, S. Sachdev, and P. Schwab for useful discussions. This work was supported by the Texas Center for Superconductivity at the University of Houston and the Robert A. Welch Foundation.

- [1] D. J. Van Harlingen, Rev. Mod. Phys. **67**, 515 (1995); D. J. Scalapino, Phys. Rep. **250**, 329 (1995).
- [2] P. W. Anderson, J. Phys. Chem. Sol. **11**, 26 (1959).
- [3] A. V. Balatsky, M. I. Salkola, and A. Rosengren, Phys. Rev. B **51**, 15547 (1995).
- [4] M. I. Salkola, A. V. Balatsky, and D. J. Scalapino, Phys. Rev. Lett. **77**, 1841 (1996).
- [5] H. Tsuchiura *et al.*, J. Phys. Soc. Jpn. **68**, 2510 (1999).
- [6] Jian-Xin Zhu *et al.*, Phys. Rev. B **61**, 8667 (2000).
- [7] A. Yazdani *et al.*, Phys. Rev. Lett. **83**, 176 (1999).
- [8] E. W. Hudson *et al.*, Science **285**, 88 (1999).
- [9] S. H. Pan *et al.*, Nature (London) **403**, 746 (2000).
- [10] Jian-Xin Zhu, C. S. Ting, and Chia-Ren Hu, Phys. Rev. B **62**, 6207 (2000); See also cond-mat/0001038.
- [11] For this issue, we are proposing a new experiment to test for this explanation, Jian-Xin Zhu *et al.* (unpublished).
- [12] M.-H. Julien *et al.*, Phys. Rev. Lett. **84**, 3422 (2000), and references therein.
- [13] L. Yu, Acta Phys. Sin. **21**, 75 (1965).
- [14] H. Shiba, Prog. Theor. Phys. **40**, 435 (1968).
- [15] M. E. Simon and C. M. Varma, cond-mat/9905349.
- [16] The spectral properties of quasiparticle excitations induced by a localized, classical magnetic moment was studied by M. I. Salkola, A. V. Balatsky, and J. R. Schrieffer, Phys. Rev. B **55**, 12 648 (1997).
- [17] L. S. Borkowski and P. J. Hirschfeld, J. Low Temp. Phys. **96**, 185 (1994); Phys. Rev. B **46**, 9274 (1992).
- [18] H. Tsuchiura *et al.*, Phys. Rev. Lett. **84**, 3165 (2000).
- [19] N. Nagaosa and P. A. Lee, Phys. Rev. Lett. **79**, 3755 (1997).
- [20] C. R. Cassanella and E. Fradkin, Phys. Rev. B **56**, 11246 (1997).
- [21] D. L. Sisson *et al.*, Phys. Rev. B **61**, 3604 (2000).
- [22] S. E. Barnes, J. Phys. F **6**, 1375 (1976); P. Coleman, Phys. Rev. B **29**, 3035 (1984).
- [23] N. Read and D. M. Newns, J. Phys. C **16**, 3273 (1983); **16**, L1055 (1983); N. Read, *ibid.* **18**, 2651 (1985).
- [24] P. Schwab and R. Raimondi, Phys. Rev. B **59**, 1637 (1999).
- [25] A. Clerk, V. Ambegaokar, and S. Hershfield, cond-mat/9901205.
- [26] A. V. Rozhkov and D. P. Arovas, cond-mat/0001062; A. Clerk and V. Ambegaokar, cond-mat/9910201.
- [27] D. Withoff and D. E. Fradkin, Phys. Rev. Lett. **64**, 1835 (1990).
- [28] K. Ingersent, Phys. Rev. B **54**, 11936 (1996).
- [29] The decoupling of the impurity makes the impurity region a hard-wall geometry boundary viewed from the conduction electrons, and its role similar to a nonmagnetic unitary impurity [6].
- [30] A. Polkovnikov, S. Sachdev, and M. Vojta, cond-mat/0007431.